



## PAPER FROM SODA-SULPHUR KOROI PULP

Md. Sirajul Karim and Md. Habibur Rahman Talukder

Department of Chemistry, Bangladesh Agricultural University, Mymensingh, Department of Chemistry, Gouripur Government College, Mymensingh

**Abstract:** Chips of suitable size of koroï were digested in an autoclave in laboratories by soda sulphur process with a view to obtaining optimum pulping conditions which were established by varying the amount of chemicals like caustic soda and sulphur, time, temperature, material-liquor ratio, etc. Emphasis was given on determining unbleached pulp-yield and permanganate number of pulp and physical properties of the brown pulp-sheets. Pulps obtained with the use of optimum pulping conditions were bleached by both CEH and CEHEH bleaching systems. Both unbleached and bleached pulps were disintegrated and beaten for 0-60 minutes and sheets were made from the different beaten samples and tested for breaking length, tear and burst factors. The brightness of the sheets and freeness of different pulps were also measured and recorded. Thus it appeared that soda-sulphur koroï pulp may be an effective source for making good quality writing and printing paper.

**Key words:** Soda sulphur, koroï, paper pulp

### Introduction

Koroï (*Albizia procera* Roxb. Benth.) is included in leguminosae family. It is a large deciduous tree, 60-80 feet high, growing over 6 feet in circumference. It is a beautiful shady tree having wide branches full of leaves. The tree is commonly distributed from the Himalayas to Bangladesh. It grows on alluvial ground along stream and other moist soil. It is also planted throughout the country along road side. Koroï is mainly used for making furniture and also used as fuel in Bangladesh by the villagers. The chemical composition of koroï was determined by Technical Association of Pulp and Paper International (TAPPI) standards (TAPPI, 1-4, 1969). It contains alpha cellulose 40.00 (%), lignin 27.16 (%), pentosan 14.02 (%) and ash 01.01 (%). As no report was available for making pulp and paper from koroï by soda sulphur process, therefore the present studies were carried out in laboratories in details.

### Materials and Methods

A rotating closed autoclave (disestor) of 20 L capacity was used for pulp making from 500 g. o.d. chips of koroï in each experiment. Optimum pulping conditions were established on the basis of the unbleached (brown) pulp-yields and permanganate number (TAPPI-5,1969) of the pulp as well as determination of physical or paper properties of the pulp sheets (TAPPI-6,1969) by varying the amounts of chemicals like caustic soda and elemental sulphur, time, temperature and material-liquor ratio. Pulps, thus obtained with the use of optimum conditions, were bleached with 3 stage CEH and 5 stage CEHEH bleaching systems where C means chlorination, E means caustic extraction and H means hypochlorite treatment. The duration of chlorination, extraction and hypochlorite treatments were for 60 minutes in each case. The consistencies were respectively 3.5%, 13.5% and 3.5% for chlorination, extraction and hypochlorite treatment. The temperature for extraction was 70-80°C and chlorination and hypochlorite treatment were carried out at room temperature. The pH of chlorination was 1-2 and that for hypochlorite solution was 9-11. Pulps were disintegrated and beaten in the Holander beater

(TAPPI-7, 1969) for 0-60 minutes of time for determination of their paper properties like breaking length, tear factor, burst factor and brightness (TAPPI 8-11, 1969). The freeness in each case was also measured (TAPPI-12, 1969).

### Results and Discussion

The unbleached pulp yield of 44.54% obtained with soda sulphur pulping of koroï was higher than those obtained by others (Karim and Sarkar, 1988). Koroï contains 40% alpha cellulose. It indicates that there was practically no loss of alpha cellulose during pulping by soda-sulphur process. It is also evident that the highest pulp yield (44.54%) for koroï was obtained with the addition of 1.0% elemental sulphur to the cooking liquor consisting of NaOH solution only. Beyond 1.0% addition, the yields increased slightly but not to an appreciable amount due to which 44.54% was considered as the highest pulp-yield in the list of the table-1. Elemental sulphur reacts with NaOH of the cooking liquor and forms Na<sub>2</sub>S which hydrolyses to NaOH and NaSH (sodium hydrosulphite). As a result, the NaOH of the cooking liquor increases. There is also formation NaSH (in the liquor) which has a good beneficial effect in pulping. The presence of NaHS acts as a buffer and tends to reduce the degrading or injurious effect of the more active NaOH on cellulose and hemicellulose thus giving rise to higher pulp yield and stronger pulps. In addition, the NaSH reacts with lignin to produce thioglignin which helps lignin more readily soluble in alkali and thus reduced cooking time from 4 hours required by other workers in pulping koroï by soda and sulphate processes (Karim 1980, Karim and Sarker, 1988) to 2.5 hours in the present studies for soda-sulphur process and thus about 40% cooking time was saved.

The permanganate number for soda-sulphur koroï pulp was found to be 14.65 which is the lowest of all the koroï pulps obtained by the previous workers (Karim 1980, Karim and Sarker, 1988). The above permanganate number showed that the pulp-yields obtained with the respective optimum conditions of pulping were not at the expense of pulp purity

indicating that the optimum cooking conditions were rightly selected and adequate for good delignification.

**Table 1 Variations in chemicals (NaOH and S), time, temperature and material liquor ratio along with permanganate number and unbleached yield of the pulp and brightness and physical or paper properties of the koroi pulp-sheets**

Experiment	NaOH (%)	Sulphur (%)	Temperature °C	Time including 50 minutes to reach temperature	Material-liquor ratio	Unbleached yield (%)	Permanganate number	Breaking length (m)	Tear factor	Burst factor	Brightness (%)
1	24.0	1.0	155	2.5	1 : 4	46.00	16.25	2419	53.09	49.35	29.6
2	26.0	1.0	155	2.5	1 : 4	44.54	14.65	2680	54.76	51.00	32.0
3	28.0	1.0	155	2.5	1 : 4	42.63	12.71	2807	50.50	53.79	35.3
4	26.0	0.0	155	2.5	1 : 4	Not well digested					
5	26.0	0.5	155	2.5	1 : 4	41.87	15.53	2641	54.01	50.49	31.5
6	26.0	1.0	155	2.5	1 : 4	44.54	14.65	2680	54.76	51.00	32.0
7	26.0	1.5	155	2.5	1 : 4	44.63	14.81	2705	54.16	51.44	32.4
8	26.0	2.0	155	2.5	1 : 4	44.70	15.03	2738	53.90	51.75	32.8
9	26.0	1.0	145	2.5	1 : 4	Not well digested					
10	26.0	1.0	155	2.5	1 : 4	44.54	14.65	2680	54.76	51.00	32.0
11	26.0	1.0	165	2.5	1 : 4	41.65	12.69	2939	49.94	57.82	35.4
12	26.0	1.0	155	1.5	1 : 4	Not digested					
13	26.0	1.0	155	2.5	1 : 4	44.54	14.65	2680	54.76	51.00	32.0
14	26.0	1.0	155	3.5	1 : 4	40.07	10.69	3200	45.51	58.55	40.5
15	26.0	1.0	155	2.5	1 : 3	Not well digested					
16	26.0	1.0	155	2.5	1 : 4	44.54	14.65	2680	54.76	51.00	32.0
17	26.0	1.0	155	2.5	1 : 5	44.32	14.40	2701	54.00	51.52	32.3

**Table 2 Optimum pulping conditions for soda-sulphur pulping of koroi along with permanganate number and unbleached pulp-yields of the pulp and brightness of the sheets**

NaOH (%)	Sulphur (%)	Temperature °C	Time in hours	Material-liquor ratio	Unbleached yield (%)	Permanganate number	Brightness (%)
26.0	1.0	155	2.5	1 : 4	44.54	14.65	32

**Table 3 Bleached pulp-yield and brightness of the 3 stage bleached CEH and 5 stage bleached CEHEH soda-sulphur koroi pulp**

Pulp	Bleached yield (%)	Brightness (%)
CEH	41.50	80.1
CEHEH	40.17	81.7


**Table 4 Fibre-dimensions of soda sulphur koroi pulp**

Pulp	Length in mm			Diameter in mm		
	Maximum	Minimum	Average	Maximum	Minimum	Average
CEH	1.52	0.68	1.09	0.030	0.015	0.021
CEHEH	1.50	0.68	1.06	0.029	0.014	0.021


200 fibres were taken for measurement.

**Table 5 Fibre-faction of soda sulphur koroi pulp**


Pulp	Fibre faction in percent (%)			
	0.50 – 0.99 mm	1.00-1.49 mm	1.50-1.99 mm	2.00-2.49 mm
CEH	40.00	60.00	0	0
CEHEH	51.46	48.54	0	0

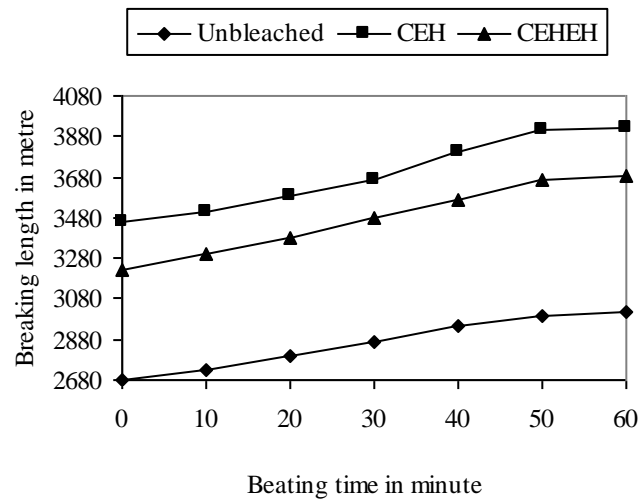


**Fig. 1.** The breaking length of the unbleached, CEH and CEHEH bleached soda sulphur koroi pulp

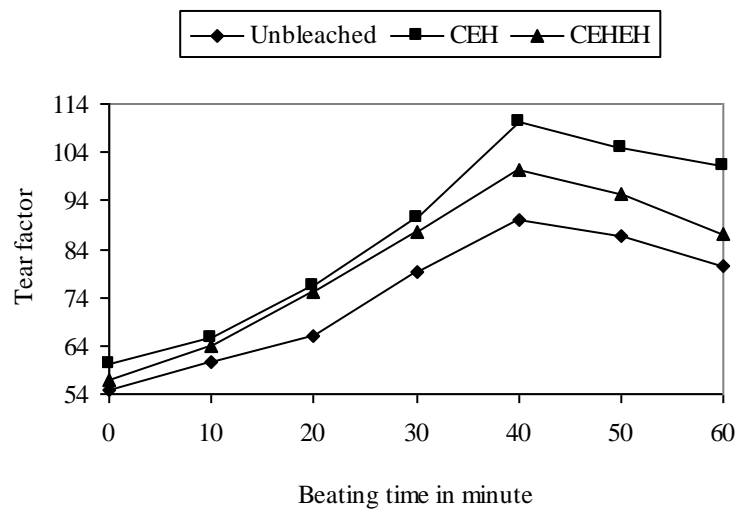


**Fig. 2.** The tear factor of the unbleached, CEH and CEHEH bleached soda sulphur koroi pulp

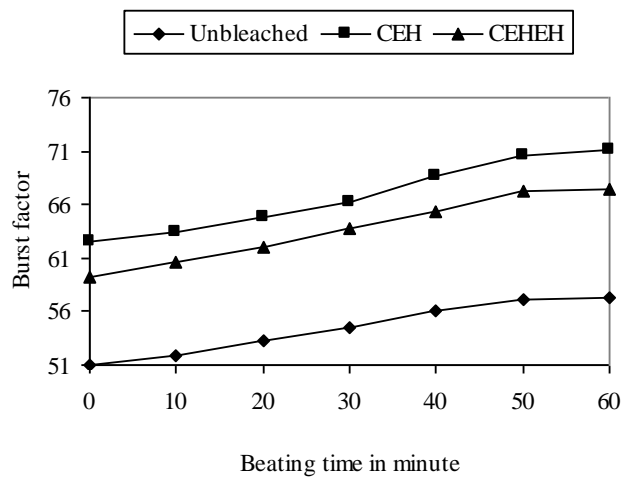

**Fig. 3.** The burst factor of the unbleached, CEH and CEHEH bleached soda sulphur koro pulp

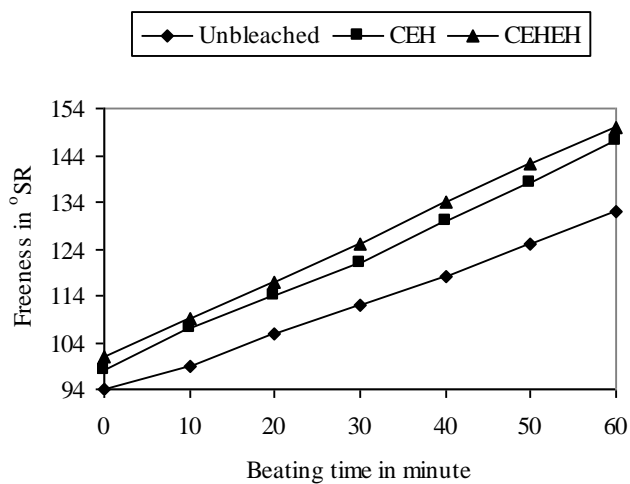

**Fig. 4.** The freeness of the unbleached, CEH and CEHEH bleached soda sulphur koro pulp

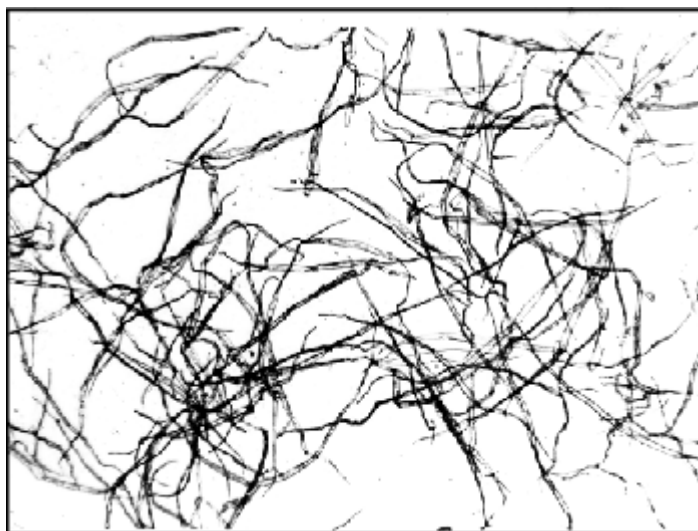

**Fig. 5.** The photomicrograph of the CEH soda-sulphur koro pulp

The unbleached pulps were bleached with CEH and CEHEH bleaching systems. The chlorine water could not improve the brightness of the chlorinated pulp due to the formation of chlorolignin, though most of the residual lignin was removed. The two brightness values for CEH and CEHEH soda sulphur koroï pulps were respectively 80.1% and 81.7% very close to Karim's values such as 80 and 81 obtained for 5 stage soda and sulphate pulps (Karim 1980, Karim and Sarker, 1988). But the above two brightness values are much above the minimum values of 70 for paper making. From the photomicrograph it has been found that the fibres were thin-walled and contained parenchyma cells. The maximum fibre length of the CEH soda sulphur koroï pulp was 1.52 mm and the minimum length was 0.68 mm. 200 fibres were taken for measurement. The average fibre length was 1.09 mm. Its diameter varied from 0.015 mm to 0.030 mm and its average diameter was 0.021 mm. 60% of the fibres were in the range of 1.00 to 1.49 mm. The fibre length of the other CEHEH soda sulphur pulp was determined as 1.06 mm. From the two values and the corresponding values for soda and sulphate bleached pulps as obtained by the other worker (Karim, 1980) it indicated that there was minimum degradation for soda-sulphur pulp not only during pulping but also during subsequent stages of bleaching. From the fibre length studies it may be concluded that koroï is a short fibre pulp.

For laboratory evaluations of their properties, the unbleached, 3 stages CEH and 5 stages CEHEH bleached pulps were beaten for 0-60 minutes of time. The breaking length and burst factors of unbleached, 3 and 5 stage bleached pulps increased from 0 to 60 minutes, though the rate of increase decreased at the end of beating like others (Karim and Siddiqueullah, 1975, Karim and Rahman, 1984, Karim and Islam 1985, Karim and Seal 2001). It is seen that the highest tear factor of soda-sulphur koroï pulp was 110.0 at its 40 minutes beating time with a freeness value of 130. The value is compared to that of 135 of jute-stick obtained with the 3 stage bleached soda-sulphur pulp at 50 minutes of beating time (Karim and Islam, 1989). The freeness of all koroï pulps of the present studies decreased during the time beating. From the overall studies it may be concluded by saying that the soda sulphur pulp of koroï is suitable for making writing and printing paper of high strength

## References

- Technical Association of Pulp and Paper International (TAPPI-1), 1969. Determination of alpha cellulose. T - 13 m - 50
- TAPPI-2, 1969. Determination of lignin. T - 15 m - 54
- TAPPI-3, 1969. Determination of pentosan. T - 17 m - 55
- TAPPI-4, 1969. Determination of ash. T - 19 m - 58
- TAPPI-5, 1969. Determination of permanganate number of pulp. T - 214 m - 56
- TAPPI-6, 1969. Beating procedures of pulps. T - 200 m - 60
- TAPPI-7, 1969. Formation of pulp sheets. T - 205 m - 61
- TAPPI-8, 1969. Determination of breaking length pulp sheets. T - 404 m - 51
- TAPPI-9, 1969. Determination of tear factor pulp sheets. T - 470 m - 52
- TAPPI-10, 1969. Determination of burst factor pulp sheets. T - 403 m - 53
- TAPPI-11, 1969. Determination of brightness of pulp sheets. T - 402 m - 49
- TAPPI-12, 1969. Determination of freeness of pulp. T - 227, m - 59
- Karim, M. S. and Sarker, A. K. 1988, Studies on pulping of koroï by soda process, Pak. J. Sci. Ind. Res. 31(2) : 150-153.
- Karim, M. S. 1980, Studies on pulping of some indigenous raw materials of Bangladesh. Ph.D. Thesis. 261-268.
- Karim, M. S. and Islam, M. A. 1989, Pak. J. Sci. Ind. Res. 32(6) : 428-429.
- Karim, M. S. and Siddiqueullah, M. 1975, Evaluation of paper making properties of the kraft and soda pulps of ekra and their blends with jute cutting. Bang. J. of Sci. Ind. Res. 89(3 & 4) : 198-190.
- Karim, M. S. and Rahman, M. A. 1984, Studies on single stage bleaching of jute sulphate pulp with sodium hypochlorite. Bang. J. Ind. Sci. Res. 19(1-4) : 91-97.
- Islam, M. A. and Karim, M. S. 1988, Bang. J. Sci. Ind. Res. 31(2) : 54-59.
- Karim, M. S. and Seal, H. P. 2001, Packing and wrapping paper from soda-sulphur pulp of wheat straw. Bang. J. Environ. Sci. 7(6) : 101-104.